INRICHTING ERKEND BIJ TOEPASSING VAN DE BESLUITWET VAN 30 JANUARI 1947 / ETABLISSEMENT RECONNU PAR APPLICATION DE L'ARRÊTE-LOI DU 30 JANVIER 1947

Royal Vriesco B.V. - A House of Happiness
Meester P.J. Troelstraweg 147-2
8919 AA LEEUWARDEN - FRIESLAND
Netherlands

Your notice of	**Your reference**	**Date**
10-06-2024		16-07-2024

Analysis Report 24.03117.01

Required tests :

EN 13773 (2003)

Sample id	Information given by the client	Date of receipt
T2411870	Boston F.R.	10-06-2024

Gina Créelle
Order responsible

This report may be reproduced, as long as it is presented in its entire form, without written permission of Centexbel.
The results of the analysis cover the received samples. Centexbel is not responsible for the representativeness of the samples.
In assessing compliance with the specifications, we did not take into account the uncertainty on the test results.

INRICHTING ERKEND BIJ TOEPASSING VAN DE BESLUITWET VAN 30 JANUARI 1947 / ETABLISSEMENT RECONNU PAR APPLICATION DE L'ARRÊTE-LOI DU 30 JANVIER 1947

Samples

T2411870
Boston F.R.

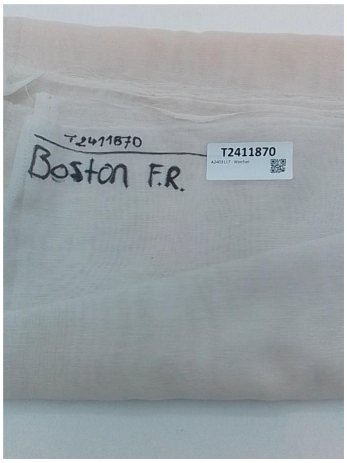

INRICHTING ERKEND BIJ TOEPASSING VAN DE BESLUITWET VAN 30 JANUARI 1947 / ETABLISSEMENT RECONNU PAR APPLICATION DE L'ARRÊTE-LOI DU 30 JANVIER 1947

Reference: T2411870 - Boston F.R.

Washing and drying

Date of ending the test	18-06-2024
Standard used	ISO 6330 (2000) + A1 (2008), ISO 6330 (2012)
Deviation from the standard	-
Conditioning	20°C, relative humidity 65%
Apparatus	Wascator FOM 71 (type A)
Used detergent	ECE detergent (Type 3)
Washing method and temperature	7A- 40°C (2000)
Drying method	A = Line dry (2000)
Number of washing cycles	1
Mass of the test specimens	230g
Mass of the ballast	The washing machine is filled with ballast to achieve 2 kg in total
Remark	Washing always occurs with a ballast type III 100% PES regardless of the composition of the fabric.

Sample generated: T2411870_01d

INRICHTING ERKEND BIJ TOEPASSING VAN DE BESLUITWET VAN 30 JANUARI 1947 / ETABLISSEMENT RECONNU PAR APPLICATION DE L'ARRÊTE-LOI DU 30 JANVIER 1947

Reference: T2411870_01d - Boston F.R.

Textiles – Burning behaviour – Curtains and drapes - Textile fabrics - Determination of the ignitability of vertically oriented specimens.

Date of ending the test	15-07-2024
Standard used	EN 1101 (1995) + A1 (2005)
Product standard	EN 13773 (2003)
Deviation from the standard	-
Conditioning	20°C, relative humidity 65%
Testing atmosphere	24°C, relative humidity 49%
Dimension of the specimens	200 mm x 80 mm
Ignition	Bottom edge

The test specimens have been cleaned.

INRICHTING ERKEND BIJ TOEPASSING VAN DE BESLUITWET VAN 30 JANUARI 1947 / ETABLISSEMENT RECONNU PAR APPLICATION DE L'ARRÊTE-LOI DU 30 JANVIER 1947

Length

Flame application time (s)	Cases of ignition	Cases of non-ignition
1	0	1
2	0	2
3	1	1
4	0	1
5	0	1
6	0	1
7	0	1
8	0	1
9	0	2
10	1	1
11	0	1
12	0	1
13	0	1
14	0	1
15	0	2
16	1	1
17	0	1
18	0	1
19	0	1
20	0	5

The mean of the recorded times at which ignition was observed is calculated
The test requires at least five instances of ignition and five instances of non-ignition.
Because less than 5 instances of ignition have been measured, and taking into account §12 of ISO 6940, a 'non-ignition' for this test is recorded

INRICHTING ERKEND BIJ TOEPASSING VAN DE BESLUITWET VAN 30 JANUARI 1947 / ETABLISSEMENT RECONNU PAR APPLICATION DE L'ARRÊTE-LOI DU 30 JANVIER 1947

Width

Flame application time (s)	Cases of ignition	Cases of non-ignition
1	0	1
2	0	1
3	0	1
4	0	1
5	0	1
10	0	1
15	0	1
20	0	5

The mean of the recorded times at which ignition was observed is calculated
No ignition within 20 s

Minimum ignition time

The test requires at least five instances of ignition and five instances of non-ignition.
Because less than 5 instances of ignition have been measured, and taking into account §12 of ISO 6940, a 'non-ignition' for this test is recorded

INRICHTING ERKEND BIJ TOEPASSING VAN DE BESLUITWET VAN 30 JANUARI 1947 / ETABLISSEMENT RECONNU PAR APPLICATION DE L'ARRÊTE-LOI DU 30 JANVIER 1947

Reference: T2411870 - Boston F.R.

Washing and drying

Date of ending the test	18-06-2024
Standard used	ISO 6330 (2000) + A1 (2008), ISO 6330 (2012)
Deviation from the standard	-
Conditioning	20°C, relative humidity 65%
Apparatus	Wascator FOM 71 (type A)
Used detergent	ECE detergent (Type 3)
Washing method and temperature	7A- 40°C (2000)
Drying method	A = Line dry (2000)
Number of washing cycles	12
Mass of the test specimens	233g
Mass of the ballast	The washing machine is filled with ballast to achieve 2 kg in total
Remark	Washing always occurs with a ballast type III 100% PES regardless of the composition of the fabric.

Sample generated: T2411870_02d

INRICHTING ERKEND BIJ TOEPASSING VAN DE BESLUITWET VAN 30 JANUARI 1947 / ETABLISSEMENT RECONNU PAR APPLICATION DE L'ARRÊTE-LOI DU 30 JANVIER 1947

Reference: **T2411870_02d - Boston F.R.**

Textiles and textile products – Burning behaviour – Curtains and drapes. Measurement of flame spread of vertically oriented specimens with large ignition source.

Date of ending the test	16-07-2024
Standard used	EN 13772 (2011)
Product standard	EN 13773 (2003)
Deviation from the standard	-
Conditioning	20°C, relative humidity 65%

The test specimens have been cleaned.

Length

	Front	Back	Front	Front
Severance1st thread	no	no	no	no
Severance 2nd thread	no	no	no	no
Severance 3rd thread	no	no	no	no
Time to sever 3rd thread (s)	/	/	/	/
Destroyed length (mm)	120	115	130	135
Flaming debris	no	no	no	no

Width

	Front	Back	Front	Front
Severance1st thread	no	no	no	no
Severance 2nd thread	no	no	no	no
Severance 3rd thread	no	no	no	no
Time to sever 3rd thread (s)	/	/	/	/
Destroyed length (mm)	110	100	110	100
Flaming debris	no	no	no	no

Classification in accordance with EN 13773 **Class 1**